arXiv:1206.2030v2 [cond-mat.supr-con] 16 Jul 2012

Anomalous impurity effects in the iron-based superconductor KFe_2As_2: evidence for a d-wave superconducting state

A. F. Wang,[1] S. Y. Zhou,[2] X. G. Luo,[1] X. C. Hong,[2] Y. J. Yan,[1] J. J. Ying,[1]
P. Cheng,[1] G. J. Ye,[1] and Z. J. Xiang,[1] S. Y. Li,[2,*] and X. H. Chen[1,†]
[1]*Hefei National Laboratory for Physical Science at Microscale and Department of Physics,*
University of Science and Technology of China, Hefei, Anhui 230026, People's Republic of China
[2]*Department of Physics, State Key Laboratory of Surface Physics,*
and Laboratory of Advanced Materials, Fudan University, Shanghai 200433, China

High-quality $K(Fe_{1-x}Co_x)_2As_2$ single crystals have been grown by using KAs flux method. Instead of increasing the transition temperature T_c through electron doping, we find that Co impurities rapidly suppress the superconductivity, with T_c down to zero at only $x \approx 0.04$. Such an effective suppression of T_c by impurities is distinctly different from that observed in $Ba_{0.5}K_{0.5}Fe_2As_2$, but mimics that in d-wave cuprate and heavy-fermion superconductors. Thermal conductivity measurements show the universal heat conduction for $x = 0$ and 0.034 superconducting samples, namely a constant residual linear term κ_0/T in zero field, despite that the scattering rate increases by 70 times. All these evidences support a d-wave superconducting state in KFe_2As_2.

PACS numbers: 74.70.Xa,74.25.fc,74.62.Dh,74.20.Rp

The iron-based superconductors, as a second high-T_c superconducting family after cuprates, have stimulated great interests [1–4]. Since the symmetry and structure of the superconducting gap reflect the underlying electron pairing mechanism, extensive works have been done to clarify them [5]. However, so far there is still no consensus on this issue, particularly the doping evolution of the superconducting gap [6, 7].

For the hole-doped $Ba_{1-x}K_xFe_2As_2$ ("122") system, the angle-resolved photoemission spectroscopy (ARPES) expeirment revealed multiple nodeless gaps at optimal doping $x = 0.4$ [8], which was further supported by measurements of bulk properties such as thermal conductivity [9]. On the overdoped side, nodeless gaps were also observed at $x = 0.7$ by ARPES [10], and at $x = 0.77$ by point contact Andreev reflection spectroscopy [11]. Surprisingly, further increasing doping to the end member KFe_2As_2, nodal superconducting gap was found by thermal conductivity, penetration depth, and NMR measurements [12–14].

While the $s_\pm$-wave gaps in $Ba_{0.6}K_{0.4}Fe_2As_2$ are still not conclusive [5], it is under hot debate whether the superconducting gap of KFe_2As_2 is d-wave with symmetry-imposed nodes [6] or s-wave with accidental nodes [7, 15]. The optimally doped $Ba_{0.6}K_{0.4}Fe_2As_2$ has both electron and hole Fermi surfaces [8], but only hole pockets are found in the extremely overdoped KFe_2As_2 [16]. In this context, the nodal gap of KFe_2As_2 may be fundamentally different from those of other iron-based nodal superconductors, such as LaFePO [17–19], $BaFe_2(As_{1-x}P_x)_2$ [20, 21], $Be(Fe_{1-x}Ru_x)_2As_2$ [22], and LiFeP [23], since all these four compounds have both electron and hole pockets. Therefore, it is of great interests to investigate whether the transition from nodeless to nodal superconducting state in $Ba_{1-x}K_xFe_2As_2$ is exactly associated with the change of Fermi-surface topology. Unfortunately, high-quality single crystals with $0.8 < x < 1.0$ are very hard to grow.

In this Letter, we try to recover the electron Fermi surface in KFe_2As_2 alternatively by Co doping, and expect the enhancement of T_c and a crossover from nodal to nodeless superconducting state. However, unexpected doping effects are found in $K(Fe_{1-x}Co_x)_2As_2$. Firstly, Co impurities suppress T_c very rapidly, and at only $x = 0.042$ no superconductivity can be observed down to 50 mK. This rapid suppression of T_c by impurities is different from that in s-wave $Ba_{0.5}K_{0.5}Fe_2As_2$, but similar to that in d-wave superconductors. Secondly, a universal heat conduction is observed for $x = 0$ and 0.034 superconducting samples. All these results point to a d-wave superconducting state in KFe_2As_2, instead of an accidental nodal s-wave.

$K(Fe_{1-x}Co_x)_2As_2$ single crystals were grown by using KAs flux method. The starting materials for single crystal growth are KAs, Fe and Co powders. KAs flux was prepared by reacting stoichiometric K pieces and As powders at 200 °C for 4 hours. KAs, Fe and Co powders were carefully weighed according to the ratio KAs: Fe: Co=12: 2-2x: 2x, with x = 0, 0.005, 0.010, 0.025 and 0.050. After thoroughly grounding, the mixtures were put into alumina crucibles and then sealed in iron crucibles under 1.5 atm of pure argon gas. The sealed crucibles were heated to 900 °C in a tube furnace filled with inert gas and kept at 900 °C for 6 hours, then cooled slowly to 600 °C at 3 °C/h to grow single crystals. The KAs flux was washed out by alcohol and shiny black crys-

---

[*] Corresponding author; Electronic address: shiyan˙li@fudan.edu.cn
[†] Corresponding author; Electronic address: chenxh@ustc.edu.cn

tals with typical dimensions of 2 × 1 × 0.03 mm^3 were obtained. The single crystals are stable in air or alcohol for several days. The actual chemical compositions were determined by energy dispersive x-ray spectroscopy to be 0, 0.017, 0.034, 0.042 and 0.050 for the five nominal compositions, with a standard instrument error 10%. Below we will use the actual compositions. Resistivity and Hall coefficient were measured in a Physical Property Measurement System (PPMS, Quantum Design). Resistivity below 2 K and thermal conductivity were measured in a dilution refrigerator.

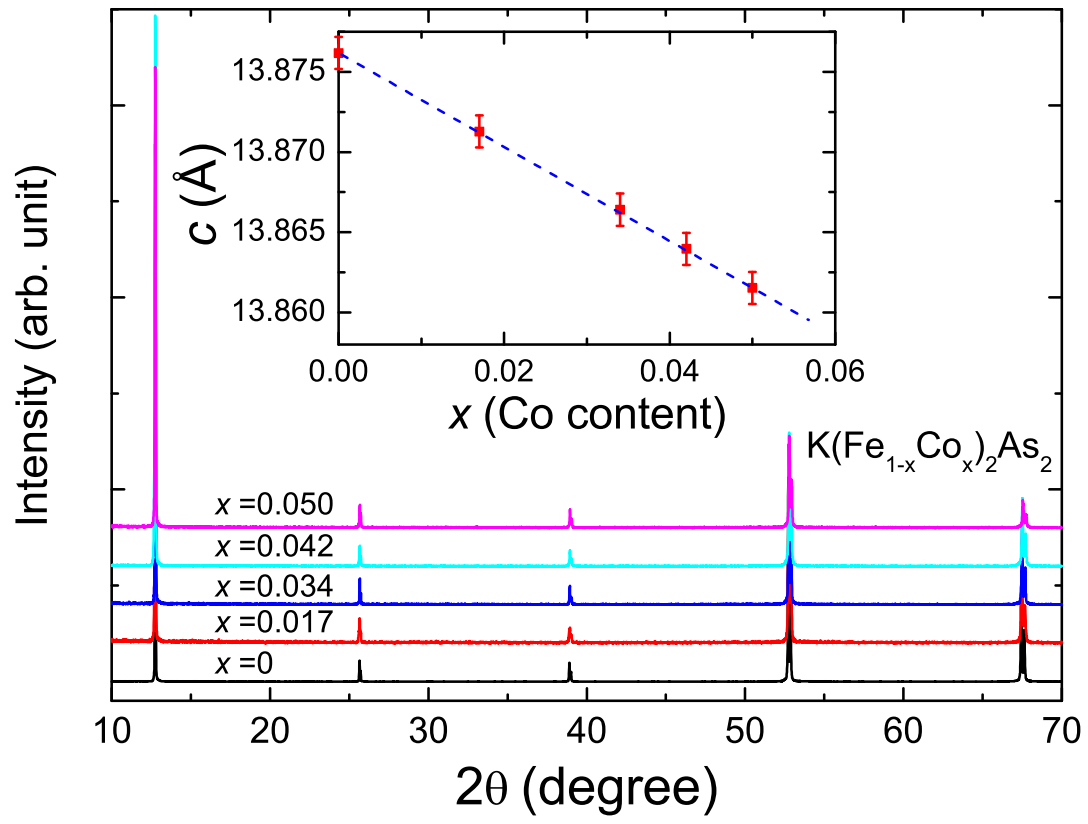

FIG. 1: (Color online) The XRD patterns for $K(Fe_{1-x}Co_x)_2As_2$ single crystals with x = 0 - 0.050. The inset shows x dependence of the lattice parameter c estimated from the data in the main panel.

Figure 1 plots the X-ray diffraction (XRD) patterns for $K(Fe_{1-x}Co_x)_2As_2$ single crystals. Only reflections of (0 0 2l) show up, suggesting good orientation along c-axis for all the crystals. The lattice parameter c was estimated from the XRD data and plotted in the inset of Fig. 1. For the pure KFe_2As_2, c = 13.876 Å is obtained, which is consistent with previous reports [24, 25]. It is found that c decreases linearly with increasing Co doping. At $x = 0.050$, c is reduced by ∼0.1%.

Figure 2 shows the temperature dependence of resistivity for $K(Fe_{1-x}Co_x)_2As_2$ single crystals. The data were taken down to 50 mK for $x = 0.042$ and 0.050 samples. The transition temperature T_c is defined when the resistivity drops to 90% of the normal-state value. For the pure KFe_2As_2, $T_c = 4.4$ K and resistivity reaches zero at 4.2 K. The power-law fit $\rho(T) = \rho_0 + bT^\alpha$ between 5 and 25 K yields a residual resistivity $\rho_0 = 0.11 \pm 0.01$ $\mu\Omega$ cm and $\alpha = 1.89$, from which a residual resistance ratio RRR = $\rho(300K)/\rho_0$ = 2017 is estimated. The extremely low ρ_0 and high RRR show that this crystal is very close to the clean limit. The RRR decreases dramatically from 2017 to 19 with increasing Co doping from 0 to 0.050 (see Table I), suggesting that the Co doping leads to large impurity scattering. At the same time, T_c decreases rapidly to zero at $x \approx 0.04$.

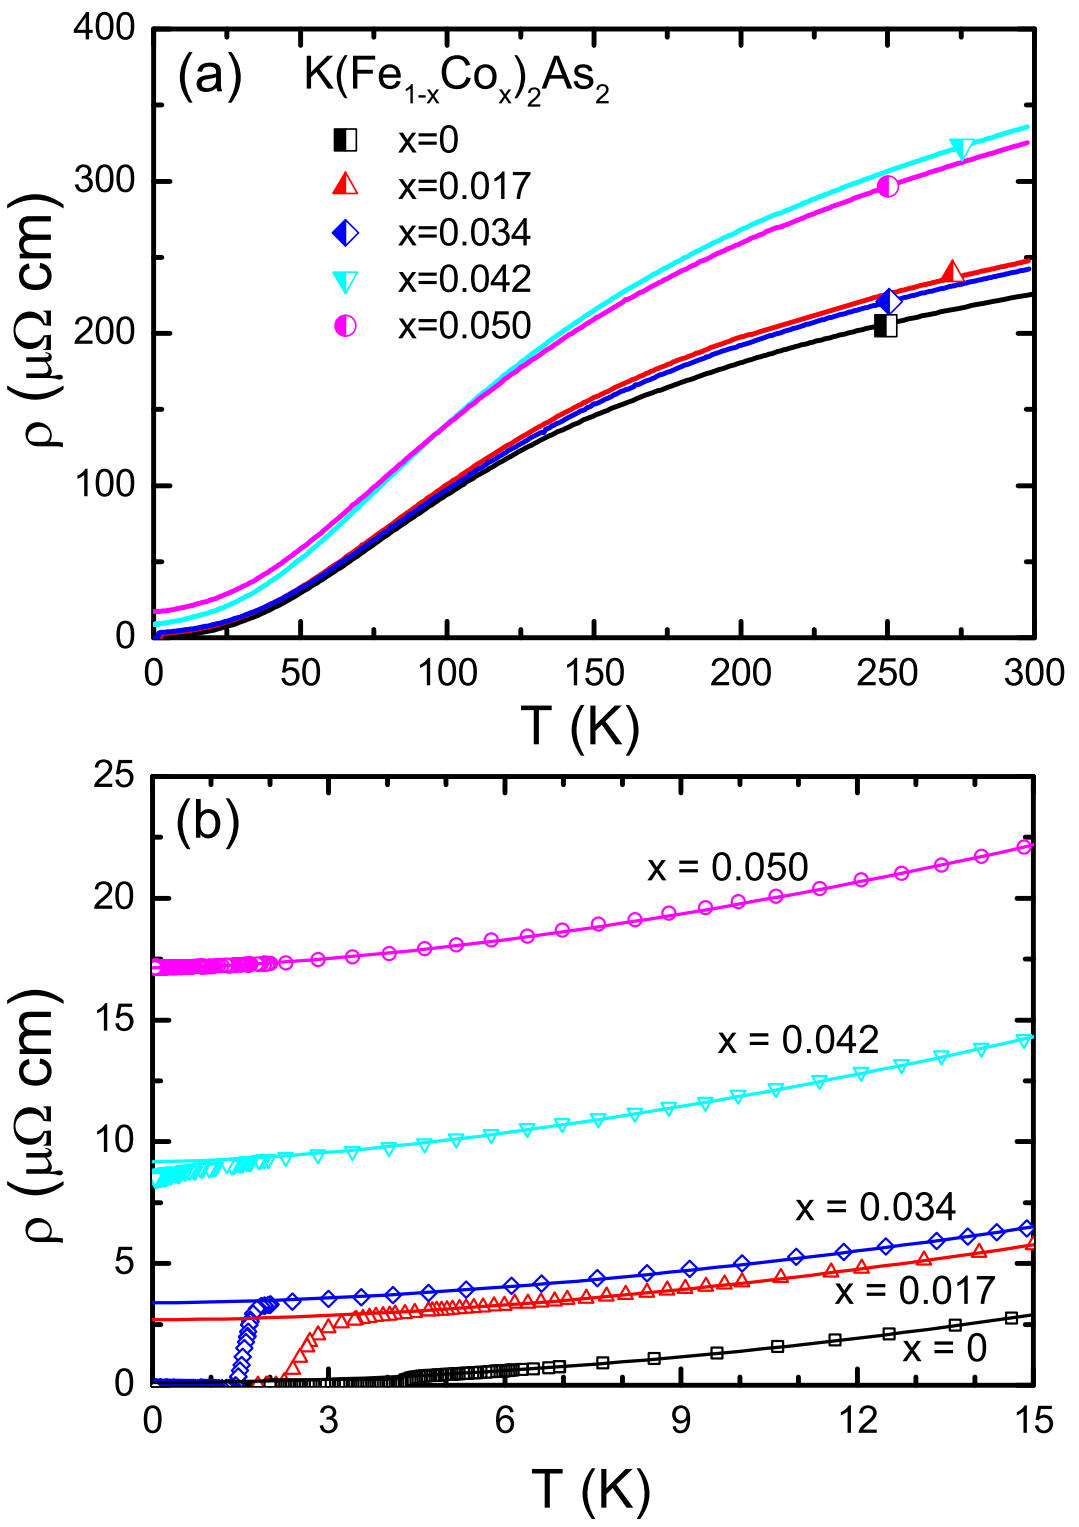

FIG. 2: (Color online) (a) Temperature dependence of resistivity for $K(Fe_{1-x}Co_x)_2As_2$ single crystals. (b) The zoomed plot for the low-temperature data shown in (a). The lines are the fits to $\rho = \rho_0 + aT^\alpha$, from which the residual resistivity ρ_0 is extrapolated.

TABLE I: Lattice parameter c, residual resistivity ρ_0, power-law exponent α, impurity scattering rate Γ, residual resistance ratio RRR and superconducting transition temperature T_c, varying with Co content x.

x	c (Å)	ρ_0 ($\mu\Omega$ cm)	α	Γ (10^{10} s^{-1})	RRR	T_c (K)
0	13.876	0.11	1.89	1.34	2017	4.4
0.017	13.871	2.69	1.79	57.6	92	2.9
0.034	13.866	3.39	1.71	100	72	1.7
0.042	13.864	9.18	1.60	296	37	0
0.050	13.862	17.1	1.62		19	0

Previously, the major role of Co doping in iron-based superconductors is to introduce electrons into the Fe_2As_2 layers, which is evident from the evolution of electron and hole pockets with x in $Ba(Fe_{1-x}Co_x)_2As_2$ [26, 27]. The impurity effect of Co dopants is less concerned. That is why we try to use Co doping to recover the electron Fermi surfaces in KFe_2As_2 and expect the increase of T_c. However, the rapid suppression of T_c with x indicates that the impurity effect of Co dopants is playing the major role in $K(Fe_{1-x}Co_x)_2As_2$.

Recently, a weak T_c suppression effect from transition-metal impurities was observed in $Ba_{0.5}K_{0.5}(Fe_{1-x}M_x)_2As_2$ (M = Mn, Ru, Co, Ni, Cu, and Zn) [28]. In Fig. 3a, we plot the normalized T_c versus Co content for $K(Fe_{1-x}Co_x)_2As_2$ and $Ba_{0.5}K_{0.5}(Fe_{1-x}Co_x)_2As_2$ [28]. For comparison, similar data of d-wave superconductors $YBa_2(Cu_{1-x}Zn_x)_3O_{6.93}$ ($T_c(x{=}0)$ = 92 K), $YBa_2(Cu_{1-x}Zn_x)_3O_{6.63}$ ($T_c(x{=}0)$ = 64.8 K), $La_{1.85}Sr_{0.15}Cu_{1-x}Zn_xO_4$ ($T_c(x{=}0)$ = 35.3 K), $La_{1.85}Sr_{0.15}Cu_{1-x}Ni_xO_4$ ($T_c(x{=}0)$ = 37.7 K), and $CeCo(In_{1-x}Sn_x)_5$ ($T_c(x{=}0)$ = 2.25 K) are also plotted [29–31]. It is clearly seen that the impurity effect on T_c in $K(Fe_{1-x}Co_x)_2As_2$ is distinctly different from that in s-wave superconductor $Ba_{0.5}K_{0.5}(Fe_{1-x}Co_x)_2As_2$, but mimics that in those d-wave superconductors.

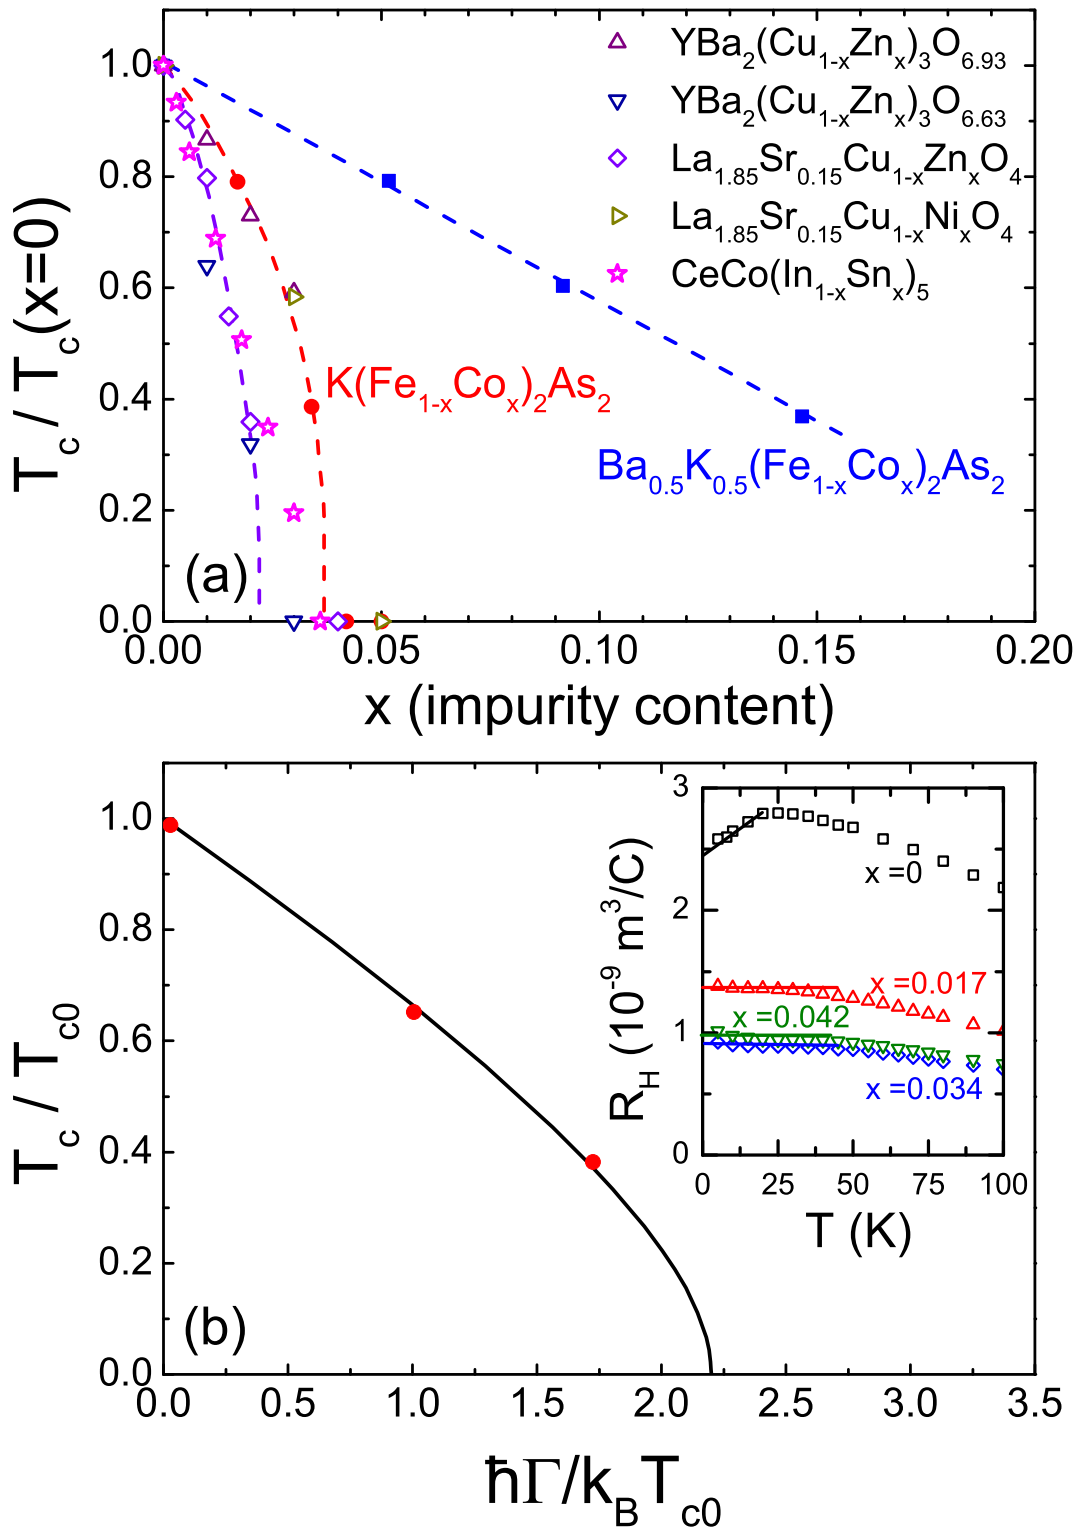

FIG. 3: (Color online) (a) The normalized T_c vs impurity content x for $K(Fe_{1-x}Co_x)_2As_2$, s-wave superconductor $Ba_{0.5}K_{0.5}(Fe_{1-x}Co_x)_2As_2$, d-wave superconductors $YBa_2(Cu_{1-x}Zn_x)_3O_{6.93}$, $YBa_2(Cu_{1-x}Zn_x)_3O_{6.63}$, $La_{1.85}Sr_{0.15}Cu_{1-x}Zn_xO_4$, $La_{1.85}Sr_{0.15}Cu_{1-x}Ni_xO_4$, and $CeCo(In_{1-x}Sn_x)_5$ [28–31]. (b) The normalized T_c of $K(Fe_{1-x}Co_x)_2As_2$ plotted as a function of scattering rate. The solid line is calculated by the Abrikosov-Gorkov formula. Inset: Low-temperature Hall coefficient for x = 0, 0.017, 0.034 and 0.042.

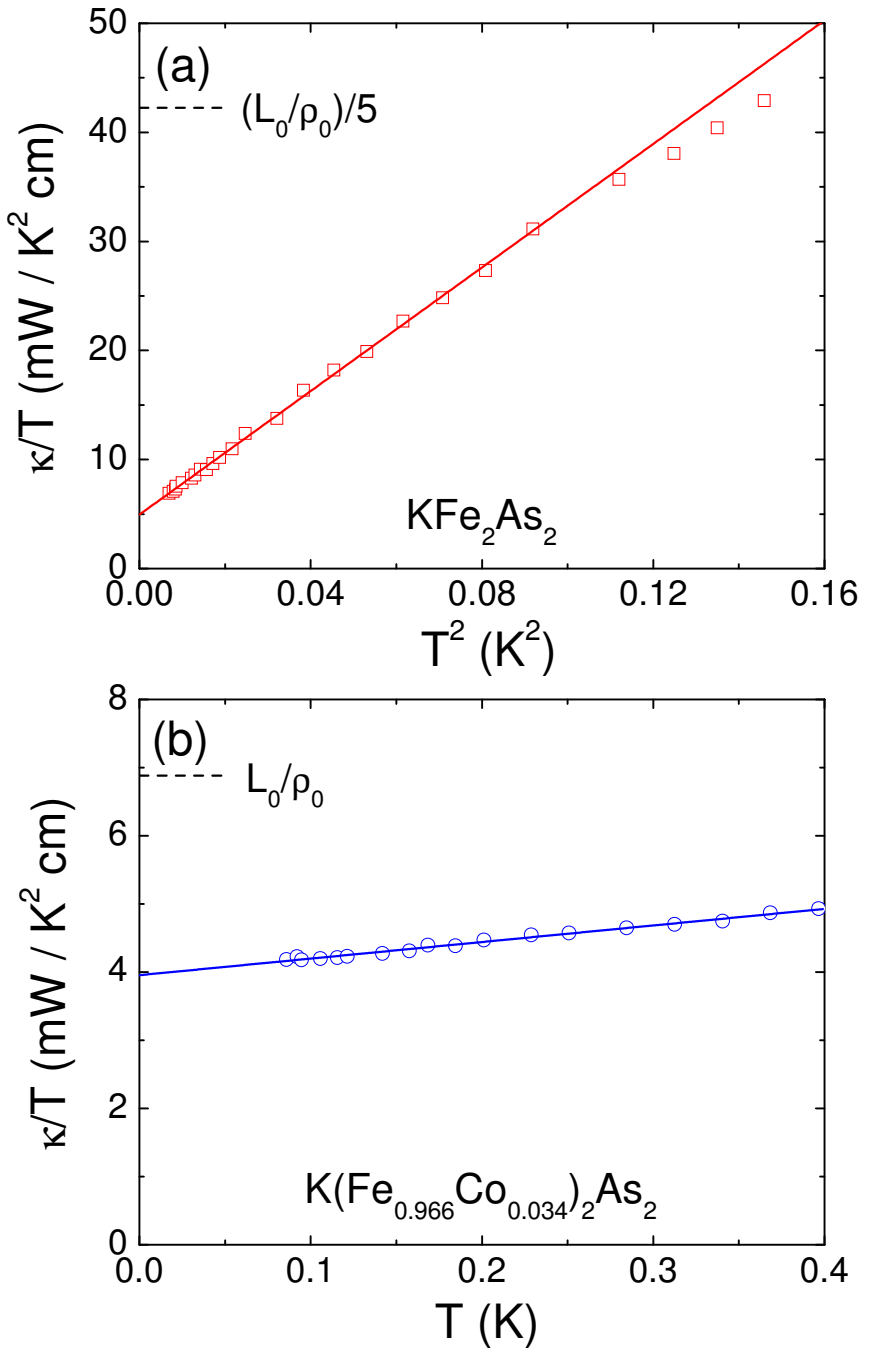

FIG. 4: (Color online) The thermal conductivity of $K(Fe_{1-x}Co_x)_2As_2$ with (a) x = 0, and (b) x = 0.034 in zero magnetic field. The solid lines are fits to $\kappa/T = a + bT^2$ for x = 0 sample, and $\kappa/T = a + bT$ for x = 0.034 sample, respectively. The dash lines are the normal-state Wiedemann-Franz law expectation L_0/ρ_0, with L_0 the Lorenz number 2.45 × 10^{-8} W Ω K^{-2} and normal-state ρ_0 = 0.116 and 3.56 $\mu\Omega$ cm, respectively. For the x = 0 sample, its L_0/ρ_0 is divided by 5 to put into the panel.

The rapid suppression of T_c by Co doping in KFe_2As_2 is very unusual among all the iron-based superconductors. If the gap of KFe_2As_2 has the same s-wave symmetry as those of $Ba_{0.5}K_{0.5}Fe_2As_2$, but with accidental nodes located somewhere on the Fermi surfaces, the impurities will make the gap more isotropic and do not effectively reduce the gap magnitude [32]. That means its T_c should not decrease in such a rapid manner. In this sense, the impurity effect on T_c of KFe_2As_2 most likely supports a d-wave superconducting gap, as pointed out earlier in Ref. [12] and theoretically demonstrated in Ref. [6].

The suppression of T_c with increasing impurity scattering rates Γ can be quantitatively described by the Abrikosov-Gorkov (AG) formula [33]. Recently, a universal rate of T_c suppression with increasing Γ, following the AG curve, was observed in optimally doped Ba-, Sr-, and Ca-based 122 systems, which indicates a common pair-breaking mechanism [34]. For our $K(Fe_{1-x}Co_x)_2As_2$, we estimate the scattering rate $\Gamma = \frac{e\rho}{m^* R_H}$, in which e is the electronic charge and m^* is the effective mass ($m^* = 6m_e$ from ARPES [16] and de Haas-van Alphen measurements [35]), from the residual resistivity ρ_0 and the extrapolated zero-temperature Hall coefficient R_H shown in the inset of Fig. 3b. The estimated Γ is listed in Table I, and plotted in Fig. 3b versus T_c. The data can be well fitted by the AG formula with T_{c0} = 4.55 K, the assumed clean-limit value. The fit gives $\hbar\Gamma_c \approx 2.2k_BT_{c0}$, where Γ_c is the critical scattering rate requested for suppressing T_c to zero. This $\hbar\Gamma_c$ is far smaller than the $45k_BT_{c0}$ in $BaFe_2As_2$ and $SrFe_2As_2$ at optimal Co, Pt, Pd, Cu, Ni and Ru doping [34], thus strongly indicates that the pairing symmetry of KFe_2As_2 is different from the s-wave symmetry in the optimally doped 122 systems.

An extraordinary feature of d-wave superconductor is the universal heat conduction upon increasing the impurity level, which has been clearly demonstrated in $YBa_2(Cu_{1-x}Zn_x)_3O_{6.9}$ [36]. The universal heat conduction results from the compensation between the increase of nodal quasiparticle density induced by impurities and the decrease of mean free path. For an accidental nodal s-wave superconductor, the heat conduction should not be universal [39].

Fig. 4 shows the thermal conductivity of superconducting $K(Fe_{1-x}Co_x)_2As_2$ single crystals with $x = 0$ and 0.034 in zero magnetic field. For the pure KFe_2As_2 with $\rho_0 = 0.116$ $\mu\Omega$ cm, the data below 0.3 K can be fitted by $\kappa/T = a + bT^2$, with the residual linear term $\kappa_0/T = a = 4.94 \pm 0.09$ mW K^{-2} cm^{-1} and $b = 283 \pm 2$. However, for the $x = 0.034$ sample with $\rho_0 = 3.56$ $\mu\Omega$ cm, the data below 0.4 K obeys $\kappa/T = a + bT$, with $\kappa_0/T = a = 3.95 \pm 0.01$ mW K^{-2} cm^{-1} and $b = 2.43 \pm 0.06$. Previously, for a dirty KFe_2As_2 with $\rho_0 = 3.32$ $\mu\Omega$ cm, similar temperature dependence of $\kappa/T = a + bT$ was observed, with $b = 3.04$ [12]. Therefore, the T^2 term of κ is attributed to phonons, and the huge T^3 term observed in the clean KFe_2As_2 must come from the nodal quasiparticles. Indeed, for a clean d-wave superconductor, theoretical calculation shows that the leading-order finite-temperature correction will contribute a T^3 term to the electronic thermal conductivity [37, 38]. Such an electronic T^3 term has been observed in ultraclean $YBa_2Cu_3O_7$ single crystal [40]. Apparently, this T^3 term is suppressed by impurities in the $K(Fe_{1-x}Co_x)_2As_2$ $x = 0.034$ sample.

The most striking observation from Fig. 4 is that while the ρ_0 and Γ are increased by 30 and 70 times, respectively, the κ_0/T of the $x = 0$ and 0.034 samples in zero magnetic field remain comparable (4.94 and 3.95 mW K^{-2} cm^{-1}). For the $x = 0$ sample, the value is less than 3% of its normal-state Wiedemann-Franz law expectation $\kappa/T = L_0/\rho_0$, with L_0 the Lorenz number 2.45×10^{-8} WΩ K^{-2}. For the dirty $x = 0.034$ sample, the value is more that 50% of its normal-state κ/T. Considering the experimental error bar, mainly coming from the uncertainty associated with geometric factor, we can say that the heat conduction in the $x = 0$ and 0.034 samples is universal. Such a universal heat conduction strongly suggests that the superconducting gap in KFe_2As_2 is d-wave, not accidental nodal s-wave. We notice that Reid *et al.* also observed universal heat conduction by comparing clean and dirty KFe_2As_2 single crystals with 10 times difference of ρ_0 [41].

In summary, we have grown high-quality $K(Fe_{1-x}Co_x)_2As_2$ single crystals and find that the superconductivity was suppressed quickly by Co doping at only $x \approx 0.04$. Such an effective suppression of T_c by impurities is very different from that in s-wave superconductor $Ba_{0.5}K_{0.5}Fe_2As_2$, but similar to that in d-wave superconductors. This result suggests the superconducting gap in KFe_2As_2 is not s-wave with accidental nodes. The observation of universal heat conduction in the $x = 0$ and 0.034 superconducting samples further supports a d-wave superconducting state in KFe_2As_2. This gap symmetry is fundamentally different from that of other 122 compounds near optimal doping, reflecting the complexity of pairing mechanism in the multi-band iron-based superconductors.

This work is supported by National Natural Science Foundation of China (Grant No. 11190021, 51021091, and 91021016), the National Basic Research Program of China (973 Program, Grant No. 2012CB922002, 2011CB00101, and 2012CB821402), Chinese Academy of Sciences, and the Program for Professor of Special Appointment (Eastern Scholar) at Shanghai Institutions of Higher Learning.

[1] Y. Kamihara *et al.*, J. Am. Chem. Soc. **128**, 10012 (2006).
[2] X. H. Chen *et al.*, Nature (London) **453**, 761 (2008).
[3] J. Paglione and R. L. Greene, Nature Phys. **6**, 645 (2010).
[4] G. R. Stewart, Rev. Mod. Phys. **83**, 1589 (2011).
[5] P. J. Hirschfeld, M. M. Korshunov, and I. I. Mazin, Rep. Prog. Phys. **74**, 124508 (2011).
[6] R. Thomale *et al.*, Phys. Rev. Lett. **107**, 117001 (2011).
[7] S. Maiti *et al.*, Phys. Rev. Lett. **107**, 147002 (2011); Phys. Rev. B **84**, 224505 (2011).
[8] H. Ding *et al.*, EPL **83**, 47001 (2008).
[9] X. G. Luo *et al.*, Phys. Rev. B **80**, 140503(R) (2009).
[10] K. Nakayama *et al.*, Phys. Rev. B **83**, 020501(R) (2011).
[11] X. H. Zhang *et al.*, Phys. Rev. B **82**, 020515(R) (2010).
[12] J. K. Dong *et al.*, Phys. Rev. Lett. **104**, 087005 (2010).
[13] K. Hashimoto *et al.*, Phys. Rev. B **82**, 014526 (2010).
[14] H. Fukazawa *et al.*, J. Phys. Soc. Jpn. **78**, 083712 (2009).
[15] K. Suzuki *et al.*, Phys. Rev. B **84**, 144514 (2011).
[16] T. Sato *et al.*, Phys. Rev. Lett. **103**, 047002 (2009).
[17] J. D. Fletcher *et al.*, Phys. Rev. Lett. **102**, 147001 (2009).
[18] C. W. Hicks *et al.*, Phys. Rev. Lett. **103**, 127003 (2009).
[19] M. Yamashida *et al.*, Phys. Rev. B **80**, 220509 (2009).
[20] Y. Nakai *et al.*, Phys. Rev. B **81**, 020503(R) (2010).
[21] K. Hashimoto *et al.*, Phys. Rev. B **81**, 220501(R) (2010).
[22] X. Qiu *et al.*, Phys. Rev. X **2**, 011010 (2012).
[23] K. Hashimoto *et al.*, Phys. Rev. Lett. **108**, 047003 (2012).
[24] K. Kihou *et al.*, J. Phys. Soc. Jpn. **79**, 124713, (2010).
[25] H. Chen *et al.*, Europhys. Lett. **85**, 17006 (2009).
[26] C. Liu *et al.*, Nature Phys. **6**, 419 (2010); Phys. Rev. B **84**, 020509 (2011).
[27] M. Neupane *et al.*, Phys. Rev. B **83**, 094522 (2011).
[28] J. Li *et al.*, Phys. Rev. B **85**, 214509 (2012).
[29] Y. Fukuzumi *et al.*, Phys. Rev. Lett. **76**, 684 (1996).
[30] C. J. Zhang and H. Oyanagi, Phys. Rev. B **79**, 064521 (2009).
[31] M. Daniel *et al.*, Phys. Rev. Lett. **95**, 016406 (2005).
[32] L. S. Borkowski and P. J. Hirschfeld, Phys. Rev. B **49**, 15404(R) (1994).
[33] A. A. Abrikosov and L. P. Gorkov, Zh. Eksp. Teor. Fiz. **39**, 1781 (1960) [Sov. Phys. JETP **12**, 1243 (1961)].

[34] K. Kirshenbaum *et al.*, arXiv:1203.5114.
[35] T. Terashima *et al.*, J. Phys. Soc. Jpn. **79**, 053702 (2010).
[36] L. Taillefer *et al.* Phys. Rev. Lett. **79**, 483 (1997).
[37] M. J. Graf *et al.* Phys. Rev. B **53**, 15147 (1996).
[38] M. J. Graf *et al.* J. Low Temp. Phys. **102**, 367 (1996).
[39] V. Mishra *et al.* Phys. Rev. B **80**, 224525 (2009).
[40] R. W. Hill *et al.* Phys. Rev. Lett. **92**, 027001 (2004).
[41] J.-Ph. Reid *et al.*, arXiv:1201.3376.